

6980 Sierra Center Parkway, Suite 90
Reno, NV 89511

March 13, 2013
File: 1009

Mr. Chris Benna
RILITE AGGREGATES
3025 Mill Street
Reno, NV 89502

RE: Rilite Pit No. 67 Concrete Aggregate

Dear Mr. Benna:

Per your request, we have performed aggregate quality testing on the aggregates delivered to our laboratory from the Rilite Pit. Test results in comparison with ASTM C33 and NDOT specifications are as follows:

Sieve Size Analysis (ASTM C136/C117)		
U.S. Standard Sieve Size	Percent By Weight Passing	
	Rilite Pit	ASTM C33/NDOT Specification
1 Inch	100	100
¾ Inch	99	90 - 100
½ Inch	73	-
¾ Inch	48	20 - 55
No. 4	3	0 - 10
No. 8	1	0 - 5
No. 200	0.2	0 - 1.0

Clay Lumps and Friable Particles (ASTM C142)	
Percent of Total Sample	ASTM C33 Specification
0.1%	2.0% Maximum

Clay Lumps (Nev. T490)	
Percent of Total Sample	NDOT Specification
0.0%	0.3% Maximum

Coal and Lignite (ASTM C123)	
Percent of Total Sample	ASTM C33 Specification
0.0%	0.5% Maximum

Lightweight Particles/Chert (ASTM C123)	
Weighted Percentage	ASTM C33 Specification
0.0%	3.0% Maximum

Mr. Chris Benna
RILITE AGGREGATES
 March 13, 2013
 Page 2

Los Angeles Abrasion (ASTM C131)	
Percentage Loss After 100 Revolutions No. 67 Stone (Grading B)	NDOT Specifications
7.1%	10% Maximum
Percentage Loss After 500 Revolutions No. 67 Stone (Grading B)	ASTM C33/NDOT Specifications
30.8%	50% Maximum

Cleanness Value (Nev. T228)	
Coarse Aggregate Sample	NDOT Specification
94	71 Minimum

Sodium Sulfate Soundness (ASTM C88/Nev. T470)	
Weighted Percentage Loss	ASTM C33/NDOT Specification
6.2%	12% Maximum


Unit Weight (ASTM C29)	
Dry Rodded Unit Weight	78.1 PCF
Dry Loose Unit Weight	72.7 PCF

Specific Gravity and Absorption (ASTM C127)	
Bulk Specific Gravity (SSD Basis)	2.30
Absorption	2.9%

We appreciate this opportunity to provide our laboratory testing services. If you have any questions or require further information, please do not hesitate to contact us.

Sincerely,

CONSTRUCTION MATERIALS ENGINEERS, INC.

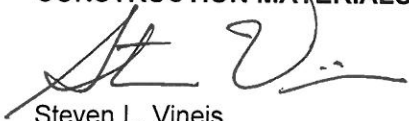

Steven L. Vineis
 Laboratory Manager
svineis@cme-corp.com
 Direct: 775-737-7568
 Direct Fax: 775-737-7605
 Mobile: 775-772-9921

Roger O. Corkill Jr., PE
 Project Coordinator
 RE Number 19868
 Expiration Date 12-31-14
rcorkill@cme-corp.com
 Direct: 775-737-7581
 Direct Fax: 775-737-7611
 Mobile: 775-722-5067



3/13/13

SLV:ROC:jy

