

6980 Sierra Center Parkway, Suite 90  
Reno, NV 89511

August 2, 2011  
File: 1009

Mr. Chris Benna  
**RILITE AGGREGATES**  
3025 Mill Street  
Reno, NV 89502

**RE: Rilite Pit – No. 8 Lightweight Aggregate**

Dear Mr. Benna:

Per your request, we have performed aggregate quality testing on the sample of Rilite Pit No. 8 aggregate received by our laboratory. Test results in comparison with ASTM C33 specifications are as follows:

Sieve Size Analysis (ASTM C136/C117)		
U.S. Standard Sieve Size	Percent by Weight Passing	
	Rilite Pit	No. 8 Aggregate ASTM C33 Specifications
½ Inch	100	100
¾ Inch	100	85 - 100
No. 4	17	10 - 30
No. 8	3	0 - 10
No. 16	2	0 - 5
No. 30	2	-
No. 200	0.9	0 - 1.0

Clay Lumps and Friable Particles (ASTM C142)	
Percent Total Sample	ASTM C33 Specification
0.6%	2.0% Maximum

Aggregate Unit Weight (ASTM C29)		
		ASTM C33 Specification
Dry Rodded Unit Weight	77.1 PCF	-
Dry Loose Unit Weight	73.7 PCF	-

Specific Gravity and Absorption (ASTM C127)	
Bulk Specific Gravity (SSD Basis)	2.26
Absorption	5.0%

Los Angeles Abrasion (ASTM C131)	
Percentage Loss After 500 Revolutions No. 8 Aggregate (Grading C)	ASTM C33 Specifications
21.0%	50% Maximum

Mr. Chris Benna  
**RILITE AGGREGATES**  
August 2, 2011  
Page 2

Cleanness Value (Nev. T228)	
Coarse Aggregate Sample	NDOT Specification
91	71 Minimum


Sodium Sulfate Soundness (ASTM C88)	
Weighted Percentage Loss	ASTM C33 Specification
7.9%	10% Maximum

Lightweight Pieces (ASTM C123)	
Percent of Total Sample	ASTM C33 Specification
0.4%	0.5% Maximum


We appreciate this opportunity to provide our laboratory testing services. If you have any questions or require further information, please do not hesitate to contact us.

Sincerely,

**CONSTRUCTION MATERIALS ENGINEERS, INC.**

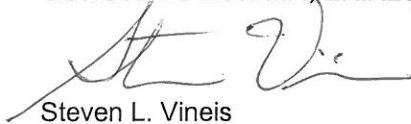

Steven L. Vineis  
Laboratory Manager  
[svineis@cme-corp.com](mailto:svineis@cme-corp.com)  
Direct: 775-737-7568  
Direct Fax: 775-737-7605  
Mobile: 775-772-9921



Jon A. Del Santo, P.E.  
Project Manager  
RE Number 17094  
Expiration Date 12-31-12  
[jdelsanto@cme-corp.com](mailto:jdelsanto@cme-corp.com)  
Direct: 775-737-7564  
Direct Fax: 775-737-7602  
Mobile: 775-846-4399

SLV:JAD:jwl

v:\active\1009\2011\no\_8\_tlwtg\_agg\_08-02-11.doc

